

Cryodur® 2357

Technical Datasheet

Chemistry

Comparable Standard: AISI S-7

Typical	C	Si	Mn	Cr	Mo	V
Analysis %	0.50	0.30	0.70	3.35	1.60	0.25

Description

Cryodur® 2357 is a shock resistant tool steel with excellent toughness and high strength.

Suitable for cold and hot work applications up to 1000°F. Supplied in the annealed condition.

Characteristics

Excellent toughness
Good wear resistance (abrasion)
Good polishability

Applications

Compression molds Tablet compression dies
Injection molds Shears
Blanking dies Punches

Physical Properties

Density: 0.280 lbs/in³ (room temperature)

Coefficient of Thermal Expansion	70°F - 400°F 6.8 x 10 ⁻⁶ /°F	70°F - 750°F 7.0 x 10 ⁻⁶ /°F	
Thermal Conductivity	68°F 200Btu/in/ft ² /hr/°F	400°F 208Btu/in/ft ² /hr/°F	750°F 215Btu/in/ft ² /hr/°F

Mechanical Properties

Compressive Strength

Hardness HRC	Approximate Compressive Strength (KSI)
55	235
60	290
62	300

Polishing

For highly cosmetic applications, the tool should be heat treated to the highest hardness possible. Size of the tool will determine the maximum hardness. A-2 polish is achievable when proper procedures are followed. A Swiss Steel representative should be consulted when determining the hardness.

Heat Treatment

Soft Annealing

Temperature	Cooling	Hardness
1130°F – 1200°F	Furnace 20°F/hr to 930°F then air cool	220 HB Max.

Stress Relieving

Condition	Temperature & Cooling
Annealed Parts	1200°F - 1250°F Hold time 2 hours, slowly cool to 930°F, then air cool
Hardened Parts	Heat to 25°F - 50°F below the original tempering temperature, hold for 2 hours, then cool in air

Hardening

Temperature	Cooling	Hardness
1690°F - 1775°F Hold at temperature for 30 minutes	Furnace quench to 350°F, air cool to 120°F. Immediately temper	60-62 Hrc Max quenched

Tempering (Double Tempering Recommended)

Temperature °F	212	392	572	752	932	1022	1112
Hardness HRC	54	54	55	56	49	46	44



Cryodur® 2357


Technical Datasheet

Tempering hardness is approximate and based on two hours at temperature.

In order to achieve faster quench rates, generous radii should be left on during rough machining.

Please contact your Swiss Steel heat treat representative for more detailed information

Tempering Diagram

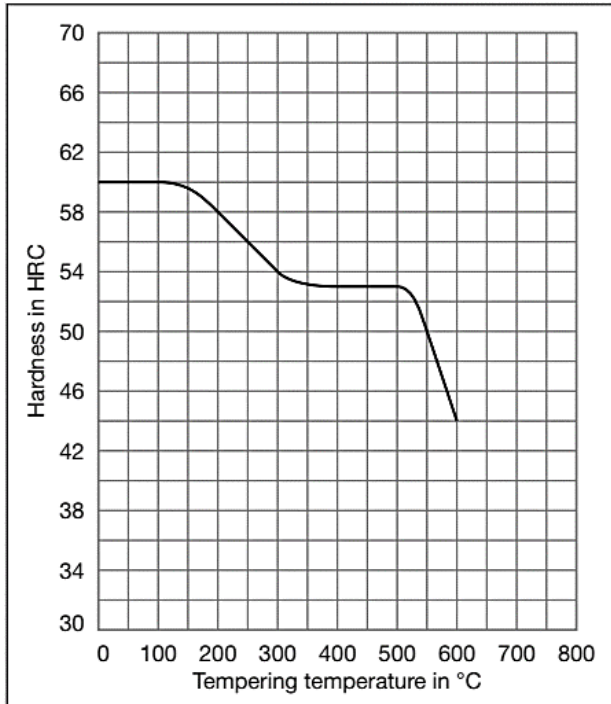

Welding

Use S7 filler material.

Condition	Preheat	Maintained Temperature during welding	Cool down to:	Post Process
Annealed	400°F - 600°F	400°F	150°F	Reanneal or temper
Hardened	25°F - 50°F below last tempering temperature	350°F	150°F	Temper 25°-50°F below last tempering temperature

General Note

All statements regarding the properties or utilization of the materials or products mentioned are for the purpose of description only. Guarantees regarding the existence of certain properties or a certain utilization are only valid if agreed upon in writing.

NORTH AMERICAN DISTRIBUTION

HEADQUARTERS + TECHNICAL SUPPORT

SWISS STEEL USA, INC.
365 Village Dr.
Carol Stream, IL 60188
Phone: 800.323.1233
Fax: 630.879.0498

MANUFACTURING + CENTRAL STOCKING FACILITY

SWISS STEEL USA, INC.
1609 E. Wilson Street
Batavia, IL 60510

DISTRIBUTION LOCATIONS

WEST COAST

556 Vanguard Way
Brea, CA 92861

MIDWEST

365 Village Dr.
Carol Stream, IL 60188

1455 Miller Pkwy.
Streetsboro, OH 44241

SOUTHEAST

119 Old Airport Rd.
Roebuck, SC 29376

NORTHEAST

370 Franklin Turnpike
Mahwah, NJ 07430

CANADA

SWISS STEEL CANADA, INC.
6350 Vipond Dr.
Mississauga, ONT L5T 1G2

www.swisssteel-international.us
www.swisssteel-international.ca